

SOR TESTING LABORATORIES, INC.

Geotechnical Engineering - Materials Testing - Forensic Studies
98 Sand Park Rd., Cedar Grove, NJ 07009
(973) 239-6001 Fax (973) 239-8380

Branch Office:
New Brunswick, NJ
(732) 494-4481

Kamil Sor, Ph.D.
Orhun Sor, P.E.
Peter G. Micklus, P.E.
Yilmaz Arhan, Ph.D.
Kenneth Rowbotham, P.E.

This report is the confidential property of the Client, and information contained may not be published or reproduced without our written permission.

Client:	The Schundler Company				
Project:	Information of Client				
Subject:	Laboratory Tests of Sprayed-on Fireproofing Material, Schundler Classic 5 LD				
Job No.:	04-504	Report No.:	04-5417A	Date:	11/23/2004

We present herewith laboratory test results of the sprayed-on fireproofing samples applied on metal deck sections in October, 2004.

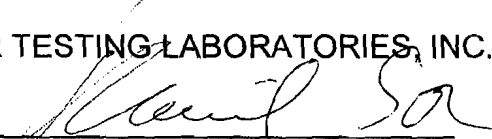
At the client's request, the samples were tested for a series of performance properties. The test methods and test results were as follows:

TEST RESULTS

Property	ASTM Method	Results
Density, lbs/cu. ft.	E-605	17.5
Compressive Strength, psi (at 10% Deformation)	E-761	110
Bond Strength, lbs/sq. ft.	E-736	350 +
Impact Resistance	E-760	Passes
Deflection Resistance	E-759	Passes
Air Erosion, grams/ft. ² /48 hours	E-859	0.000
Thickness, inches	E-605	1.13
Corrosion, grams/mm ²	E-937	0.00

Very truly yours,

SOR TESTING LABORATORIES, INC.


Kamil Sor, Ph. D.
President

KS/ls
cc: (1) Client, Attn: Bruce Schundler
Fax 732-287-4185